

# Polypyrenes as High-Performance Cathode Materials for Aluminum Batteries

**Journal Article****Author(s):**

Walter, Marc; Kravchyk, Kostiantyn V.; Böfer, Cornelia; Widmer, Roland; Kovalenko, Maksym V.

**Publication date:**

2018-04-12

**Permanent link:**

<https://doi.org/10.3929/ethz-b-000260955>

**Rights / license:**

[Creative Commons Attribution-NonCommercial 4.0 International](#)

**Originally published in:**

Advanced Materials 30(15), <https://doi.org/10.1002/adma.201705644>

# Polypyrenes as High-Performance Cathode Materials for Aluminum Batteries

Marc Walter, Kostiantyn V. Kravchuk, Cornelia Böfer, Roland Widmer, and Maksym V. Kovalenko\*

The pressing need for low-cost and large-scale stationary storage of electricity has led to a new wave of research on novel batteries made entirely of components that have high natural abundances and are easy to manufacture. One example of such an anode–electrolyte–cathode architecture comprises metallic aluminum,  $\text{AlCl}_3\text{:}[\text{EMIm}]\text{Cl}$  (1-ethyl-3-methylimidazolium chloride) ionic liquid and graphite. Various forms of synthetic and natural graphite cathodes have been tested in recent years in this context. Here, a new type of compelling cathode based on inexpensive pyrene polymers is demonstrated. During charging, the condensed aromatic rings of these polymers are oxidized, which is accompanied by the uptake of aluminum tetrachloride anions ( $\text{AlCl}_4^-$ ) from the chloroaluminate ionic liquid. Discharge is the fast inverse process of reduction and the release of  $\text{AlCl}_4^-$ . The electrochemical properties of the polypyrenes can be fine-tuned by the appropriate chemical derivatization. This process is showcased here by poly(nitropyrene-*co*-pyrene), which has a storage capacity of  $100 \text{ mAh g}^{-1}$ , higher than the neat polypyrene ( $70 \text{ mAh g}^{-1}$ ) or crystalline pyrene ( $20 \text{ mAh g}^{-1}$ ), at a high discharge voltage ( $\approx 1.7 \text{ V}$ ), energy efficiency ( $\approx 86\%$ ), and cyclic stability (at least 1000 cycles).

electric grid.<sup>[1,2]</sup> Toward this goal, rechargeable battery technologies based on highly abundant metals, such as Na,<sup>[3–5]</sup> Mg,<sup>[6–10]</sup> and Al,<sup>[11–24]</sup> as charge carriers and/or electrodes have come into a major research spotlight. In particular, batteries that employ metallic Al on the anodic side harness numerous advantages, such as high natural abundance, high theoretical charge-storage capacity, and high safety.<sup>[25]</sup> Unlike metallic Li or Na, Al can be safely used as an anode due to smooth, fast, and dendrite-free electrodeposition in ionic liquids.<sup>[26–30]</sup> Thus, various rocking-chair-type aluminum cathodes are currently being explored in respect to the reversible insertion of  $\text{Al}^{3+}$  ions.<sup>[11–17,19–22,31]</sup> However, it is extremely difficult to intercalate/deintercalate highly charged  $\text{Al}^{3+}$  ions in any host structure because of the high ionic charge density ( $\text{Al}^{3+}$  is even smaller than  $\text{Li}^+$ ), which renders low ionic diffusivity and causes other difficulties such as the sol-

vation and desolvation of ions.<sup>[32]</sup> In contrast, the facile reversible intercalation is afforded with monovalent species, such as  $\text{AlCl}_4^-$ . This was shown in recent publication by Dai group in 2015,<sup>[24]</sup> wherein porous artificial graphite can be reversibly electrochemically oxidized/reduced in  $\text{AlCl}_3\text{:}[\text{EMIm}]\text{Cl}$  ionic liquid (EMIm being 1-ethyl-3-methylimidazolium chloride) for thousands of cycles with concomitant intercalation/deintercalation of  $\text{AlCl}_4^-$  ions within the graphene layers. In recent years, intense efforts have been devoted to unravel the structure–electrochemical property relationship for various graphites obtained synthetically<sup>[24,33–39]</sup> or from nature,<sup>[40–46]</sup> showing charge-storage capacities of  $60\text{--}150 \text{ mAh g}^{-1}$  at average discharge voltages of  $1.6\text{--}2 \text{ V}$ .

In this work, the focus is shifted from the graphitic materials to the conjugated polymeric cathodes. Such organic electrode materials are very attractive for rechargeable batteries because they are flexible, lightweight, low-cost, and safe for the environment.<sup>[47–50]</sup> Electrochemical cycling performance of conducting polymers for aluminum batteries comprising  $\text{AlCl}_3\text{:}[\text{EMIm}]\text{Cl}$  ionic liquid was demonstrated only once by Hudak,<sup>[51]</sup> using polypyrrole and polythiophene as  $\text{AlCl}_4^-$  anion-insertion cathodes. The idea that inspired this work was to emulate the cathodic behavior of the infinitely large polyaromatic graphite layers ( $\text{sp}^2$ -hybridized carbons) using only a few condensed aromatic rings. Molecular pyrene ( $\text{C}_{16}\text{H}_{10}$ ), containing four condensed aromatic rings,

Switching from fossil fuels to renewable,  $\text{CO}_2$ -emission-free energy sources (e.g., solar or wind power) remains a great challenge due to the intermittent nature of the latter sources; consequently, large-scale energy storage solutions are needed to allow a stable energy supply and integration into the

Dr. M. Walter, Dr. K. V. Kravchuk, C. Böfer, Prof. M. V. Kovalenko  
Department of Chemistry and Applied Biosciences  
Laboratory of Inorganic Chemistry  
ETH Zürich

Vladimir-Prelog-Weg 1, CH-8093 Zürich, Switzerland  
E-mail: mvkovalenko@ethz.ch


Dr. M. Walter, Dr. K. V. Kravchuk, C. Böfer, Prof. M. V. Kovalenko  
Laboratory for Thin Films and Photovoltaics  
Empa – Swiss Federal Laboratories for Materials Science and Technology  
Überlandstrasse 129, CH-8600 Dübendorf, Switzerland

Dr. R. Widmer  
Nanotech@surfaces Laboratory  
Empa – Swiss Federal Laboratories for Materials Science and Technology  
Überlandstrasse 129, CH-8600 Dübendorf, Switzerland

 The ORCID identification number(s) for the author(s) of this article can be found under <https://doi.org/10.1002/adma.201705644>.

© 2018 The Authors. Published by WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim. This is an open access article under the terms of the Creative Commons Attribution-NonCommercial License, which permits use, distribution and reproduction in any medium, provided the original work is properly cited and is not used for commercial purposes.

DOI: 10.1002/adma.201705644

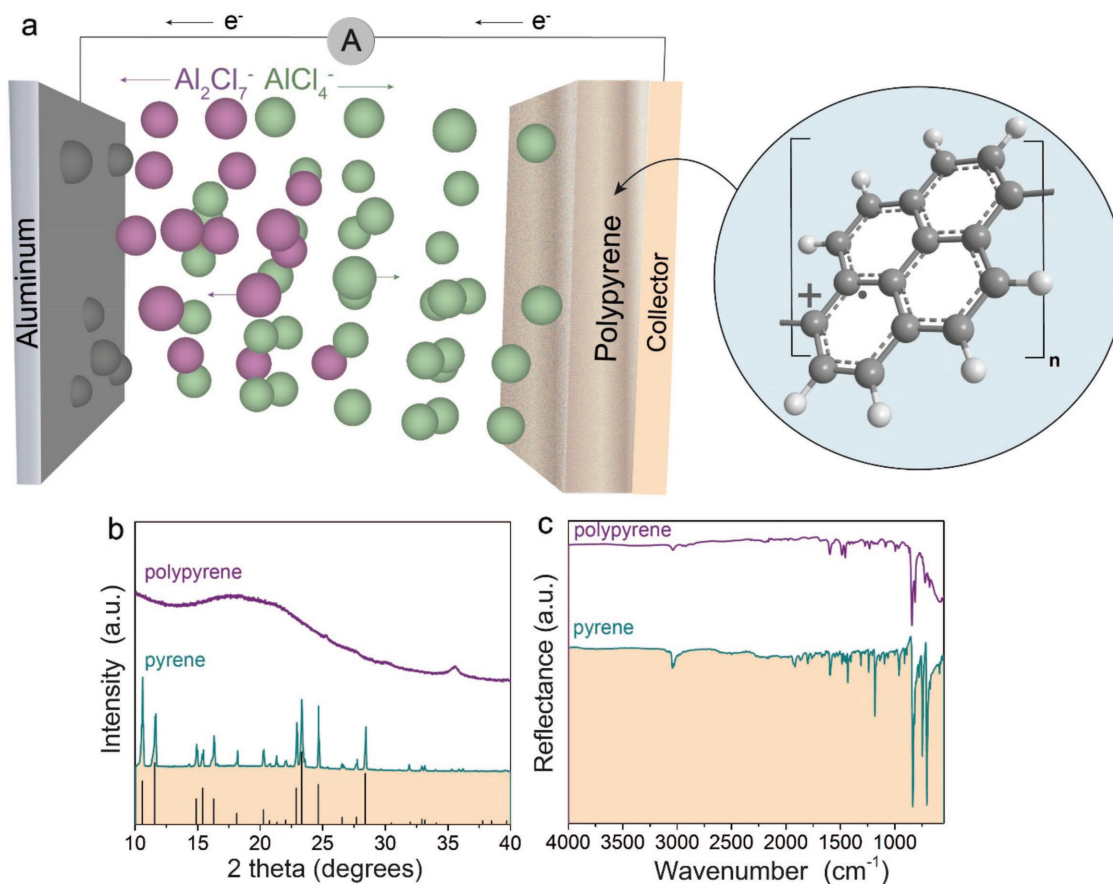

**Figure 1.** a) Schematic of the working principle of a rechargeable aluminum battery during charge with a polypyrrene cathode and chloroaluminate ionic liquid. b) XRD pattern of crystalline pyrene (indexed to a known monoclinic polymorph; PDF entry No. 00-024-1855) and c) FTIR spectra of pyrene and polypyrrene.

was selected for this study, and the electrochemical properties of its monomeric and polymeric forms are compared herein. This choice for the organic cathodic material was motivated by the known p-type redox activity of these materials at relatively high redox potentials, which makes them potentially useful for storage of lithium and sodium ions.<sup>[52,53]</sup> Upon electrooxidation, pyrene can, on average, acquire up to one positive charge per four aromatic rings to generate a radical cation, and this charge can be counterbalanced by the intercalation of  $\text{AlCl}_4^-$  anions from the ionic liquid (Figure 1a). Upon electroreduction of the polymer, the anions are released back into the ionic liquid. The corresponding theoretical charge-storage capacity is  $133 \text{ mAh g}^{-1}$  (based on one electron per pyrene unit), on par with the best values for graphites. In addition, we point to the fact that intercalation of large anions, such as  $\text{AlCl}_4^-$  is difficult to accomplish with conventional crystalline materials, but is a unique opportunity for materials with much greater structural flexibility such as pyrene-based derivatives. Moreover, pyrene is an inexpensive material available by distillation of coal tar and is used commercially in large quantities for producing dyes and dye precursors.<sup>[54]</sup> In fact, in view of the economic efficiency of the employment of aluminum batteries for grid-scale electricity storage, it is of paramount importance to utilize low-cost, earth-abundant, and easy to produce components. Herein, we report that polypyrrene and its derivative poly(nitropyrene-co-pyrene) can serve as highly reversible and high-capacity cathode

materials for aluminum batteries, experimentally delivering capacities of 70 and  $100 \text{ mAh g}^{-1}$ , respectively, at an average voltage of 1.7 V. The poly(nitropyrene-co-pyrene) was also found to have a high cycling stability (at least 1000 cycles) at a current density of  $200 \text{ mA g}^{-1}$ .

Polypyrrene was synthesized according to the oxidative polymerization procedure reported by Li et al.<sup>[55]</sup> (see Figure S1, Supporting Information). As shown in Figure 1b, unlike the crystalline pyrene precursor, the obtained product is almost fully amorphous. The polymerization of pyrene was further confirmed by the Fourier transform infrared (FTIR) spectra (Figure 1c). In particular, significantly lower intensities of the signals at 1184, 748, and  $706 \text{ cm}^{-1}$ , which are associated mainly with C–H deformations, and the C–H stretching vibration at  $3040 \text{ cm}^{-1}$ , indicate fewer C–H bonds as a result of the polymerization (substitution of C–H with C–C bonds).<sup>[55,56]</sup> For the electrochemical tests, electrodes were prepared by mixing pyrene or polycyclic pyrene derivatives with carbon black (CB), polyvinylidene fluoride (PVdF), and *N*-methylpyrrolidone (NMP), and the resulting slurries were cast onto tungsten current collectors. A custom-made cell was employed for the electrochemical tests (Figure S2, Supporting Information). The cell consisted of aluminum (anodic side) and tungsten (cathodic side) current collectors inside a plastic housing. Tungsten was chosen as current collector material due to its high oxidation stability (see Figure S3, Supporting Information);

other common metals such as stainless steel undergo fast corrosion in  $\text{AlCl}_3$ -based ionic liquids. The electrodes were moderately pressed on to either side of a glass-fiber separator that was soaked with carefully dried chloroaluminate ionic liquid (mixture of  $[\text{EMIm}]\text{Cl}$  with  $\text{AlCl}_3$ , molar ratio 1.3:1).


The working principle of the aluminum battery presented herein, as depicted in Figure 1a, can be represented by the following cathodic and anodic half reactions during charge



Reaction (1) represents intercalation of  $\text{AlCl}_4^-$  into polypyrene during its oxidation.<sup>[57]</sup> Reaction (2) shows electro-deposition of Al on the anode side. The charge-storage mechanism proposed in Reaction (1) assumes that the only active intercalant species is  $\text{AlCl}_4^-$ . As follows from X-ray photoelectron spectroscopy (XPS) measurements, intercalation of  $\text{AlCl}_4^-$  ions into polypyrene was evident from the appearance of both Al 2p and Cl 2p peaks after electrochemical charging (Figure S4a,b, Supporting Information). Additionally, energy-dispersive X-ray spectroscopy (EDX) analysis of charged

polypyrene electrodes revealed the appearance of Al  $K\alpha$  and Cl  $K\alpha$  peaks (Figure S4c,d, Supporting Information). However, taking into account that chloroaluminate ionic liquid contains a mixture of  $\text{AlCl}_4^-$ ,  $\text{Al}_2\text{Cl}_7^-$ , and free  $\text{Cl}^-$  ions, intercalation of all three ions into polypyrene network during charge is possible.

Figure 2 shows the electrochemical performance of electrodes composed of pyrene and polypyrene as cathode materials in aluminum batteries at a high current density ( $200 \text{ mA g}^{-1}$ ). In the case of polypyrene, the capacity initially decreases, but then remains stable for 300 cycles at  $\approx 70 \text{ mAh g}^{-1}$ , which corresponds to more than half of the theoretical value based on a one-electron redox process at the pyrene unit ( $133 \text{ mAh g}^{-1}$ , see calculations of theoretical capacity in the Supporting Information). Galvanostatic charge–discharge curves reveal that the storage capacity corresponds to a relatively high discharge voltage of  $\approx 1.7 \text{ V}$  (Figure 2b). It has to be noted that electrochemical performance of polypyrene depends on the acidity of chloroaluminate ionic liquid (molar ratio of  $\text{AlCl}_3$ : $[\text{EMIm}]\text{Cl}$ ). As electrochemical data indicate (Figure S5, Supporting Information), the optimal molar ratio of  $\text{AlCl}_3$ : $[\text{EMIm}]\text{Cl}$  is  $\approx 1.3$ . In comparison to polypyrene, the performance of monomeric pyrene is quite poor. In particular, the initial discharge capacity of pyrene is only  $20 \text{ mAh g}^{-1}$  and decreases rapidly to  $\approx 10 \text{ mAh g}^{-1}$  in subsequent cycles. Such a

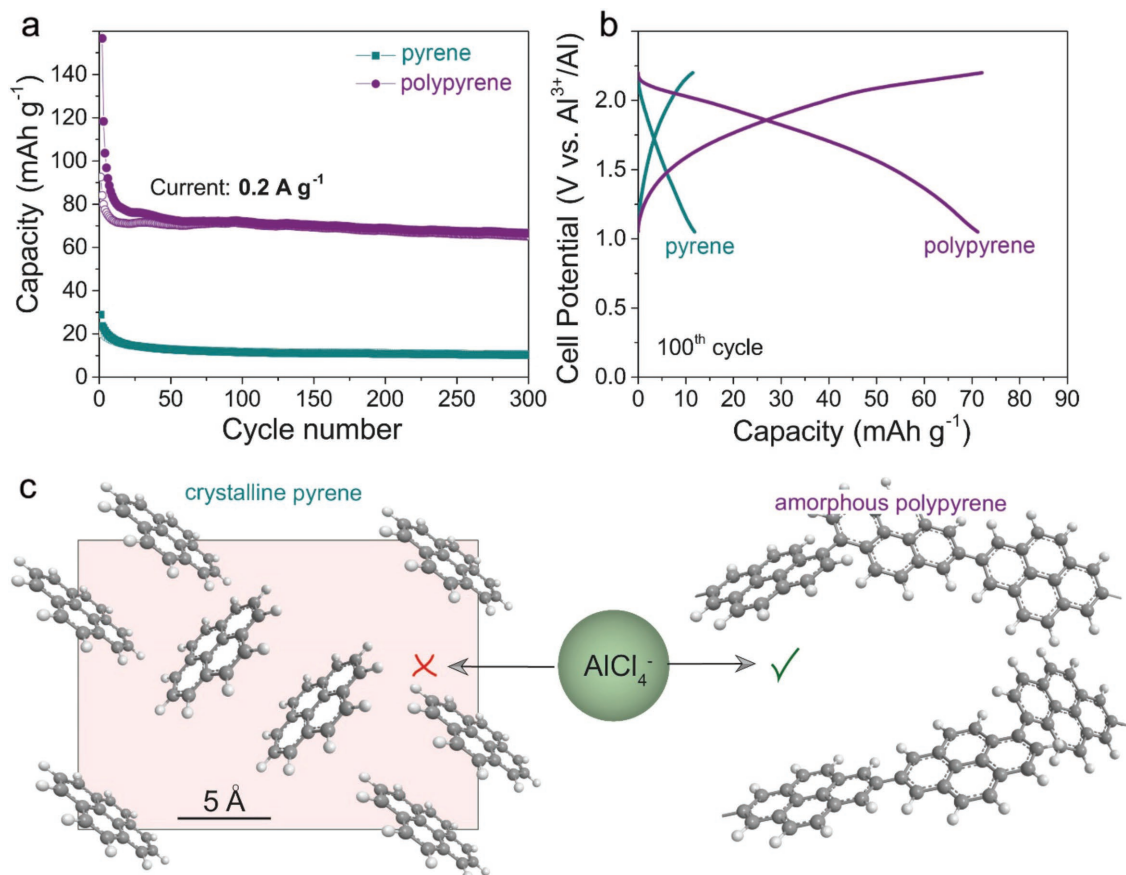

**Figure 2.** Electrochemical performance of aluminum batteries with pyrene and polypyrene as cathode materials: a) capacity retention upon cycling and b) corresponding charge–discharge voltage profiles for the 100th cycle. Cells were cycled at room temperature at a current density of  $200 \text{ mA g}^{-1}$  (referring to the mass of the polymer) in the potential range of 1.05–2.2 V. c) Schematic representation of the structural differences between pyrene (crystalline, e.g., dense molecular packing) and polypyrene (amorphous, porous, and flexible), which impact their  $\text{AlCl}_4^-$  storage behavior.


drastic difference in the electrochemical performance of pyrene and polypyrene can be attributed to several factors. Compared with its polymeric counterpart, pyrene not only is more prone to dissolution in the chloroaluminate ionic liquid but also is more electronically insulating due to the lack of an extended conjugated  $\pi$ -system. Furthermore, effective insertion of  $\text{AlCl}_4^-$  is hindered by the tight packing of molecules in the crystalline pyrene. Its intermolecular distances of 3.5–4 Å<sup>[58]</sup> are too small for the diffusion of the large  $\text{AlCl}_4^-$  ions (5.3–5.9 Å).<sup>[24,59]</sup> In contrast, an amorphous and flexible arrangement of polypyrene chains allows for diffusion of  $\text{AlCl}_4^-$  ions.

To assess the impact of electron-withdrawing substituents on the electrochemical performance, a copolymer of 1-nitropyrene and pyrene was synthesized using the aforementioned synthesis procedure, but with both compounds as starting materials in a 1:1 molar ratio. The resulting product was amorphous (Figure S6, Supporting Information) and shows almost the same FTIR spectrum as polypyrene with the main difference being additional vibrations at 1510 and 1330  $\text{cm}^{-1}$  (Figure 3a). These additional vibrations can be attributed to the vibrations of  $\text{NO}_2$  groups, specifically the N=O asymmetric stretches (typically found at 1660–1490  $\text{cm}^{-1}$ ) and N=O symmetric stretches (typically found at 1390–1260  $\text{cm}^{-1}$ )<sup>[60]</sup> (see also Figure S7, Supporting Information), which indicates the successful formation of a copolymer of pyrene and 1-nitropyrene.

C, H, and N elemental analysis suggested an atomic ratio C:N of 45:1, corresponding to approximately three pyrene per  $\text{NO}_2$  group. Hence, the number of nitropyrene units in the

poly(nitropyrene-co-pyrene) is lower than one would expect based on a 1:1 mixing ratio of monomers before polymerization. Regarding molecular weight determination, it should be noted that much like polypyrene,<sup>[55]</sup> the poly(nitropyrene-co-pyrene) is poorly soluble in common organic solvents. Gel permeation chromatography (GPC) with tetrahydrofuran as the eluent revealed that in the case of both polypyrene and poly(nitropyrene-co-pyrene), the soluble fraction contains mostly oligomeric species with fewer than 10 repeating units (Figure S8, Supporting Information).

Figure 3b–d summarizes the results of the electrochemical tests with poly(nitropyrene-co-pyrene) as the cathode material in aluminum batteries carried out at a current density of 200  $\text{mA g}^{-1}$  and in the potential range of 1.05–2.2 V. Similar to polypyrene, almost no capacity fading was observed for 100 cycles with a stable average discharge voltage of  $\approx 1.7$  V. Relatively high coulombic efficiencies ( $\approx 97\%$ ) and energy efficiencies (86%) were obtained. Furthermore, even at a high charging–discharging rate (2000  $\text{mA g}^{-1}$ ), poly(nitropyrene-co-pyrene) shows minimal capacity fading after 500 cycles with an average capacity of  $\approx 48$   $\text{mAh g}^{-1}$  (Figure S9, Supporting Information). Interestingly, the poly(nitropyrene-co-pyrene) shows significantly higher capacities than the polypyrene sample, yet the profile of the galvanostatic charge and discharge curves remains almost the same (Figure 3c), indicating that the introduction of  $\text{NO}_2$  groups is likely not significant for the redox potential. Plausible explanations for the higher observed capacity are that the poly(nitropyrene-co-pyrene) shows better

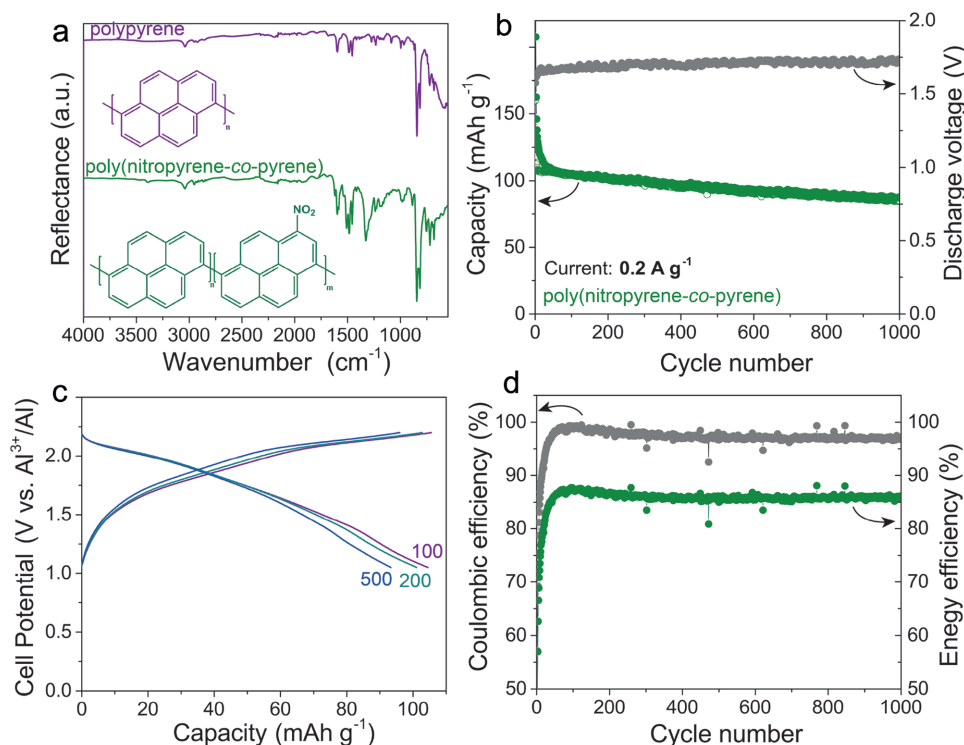

**Figure 3.** a) FTIR spectra of polypyrene (purple) and poly(nitropyrene-co-pyrene) (green). Electrochemical performance of aluminum batteries with poly(nitropyrene-co-pyrene) as the cathode material: b) capacity retention upon cycling and average discharge voltages, c) corresponding charge–discharge voltage curves for the 100th, 200th, and 500th cycles, and d) Coulombic and energy efficiencies. Cells were cycled at room temperature at a current density of 200  $\text{mA g}^{-1}$  in the potential range of 1.05–2.2 V.

dispersibility in NMP than the homopolymer and is therefore in potentially better contact with the conductive additive (CB) or that there are structural differences between the homopolymer and copolymer (e.g., spacing between the polymer chains, porosity, etc.) that lead to utilization of a higher fraction of the active material. However, it should be noted that much poorer battery performance was observed for materials obtained by polymerization of only 1-nitropyrene (Figure S10, Supporting Information). Thus far, the only reported work on polymers as cathodes for aluminum batteries utilizes polythiophene and polypyrrole,<sup>[51]</sup> and identical cells with Al and AlCl<sub>3</sub>:[EMIm]Cl were assembled. However, these polymers showed lower discharge voltages and worse cyclabilities and rate capabilities than poly(nitropyrene-co-pyrene) (see Table S1, Supporting Information for detailed comparison).

The electrochemical performances of polycyclic pyrene derivatives are on par with the performances of graphitic materials, which exhibit capacities of 60–150 mAh g<sup>-1</sup> and average discharge voltages of 1.6–2.0 V, exemplifying the great utility of polymeric materials and in particular copolymers for aluminum batteries. The unique features of polycyclic aromatic polymers, such as their low cost, lightweight, flexibility, and solution processability,<sup>[54,61]</sup> might offer new opportunities in low-cost battery technologies.

In summary, we have demonstrated a proof-of-concept for aluminum batteries with inexpensive pyrene-based polymers as high-performance cathode materials. Whereas crystalline monomeric pyrene shows insignificant charge-storage capacities, good electrochemical performances were obtained with amorphous polypyrene, which could be further improved by using a copolymer of pyrene and nitropyrene. In particular, stable cycling with an average capacity of 100 mAh g<sup>-1</sup> and a discharge voltage of 1.7 V for 1000 cycles at a current density of 200 mA g<sup>-1</sup> was demonstrated for poly(nitropyrene-co-pyrene) with high coulombic efficiency (97–98%) and energy efficiency (86%). We note that prior to practical application of this class of materials, substantial further work is needed, particularly on understanding the atomistic details of charge-storage and fading mechanisms, as well as optimization of the electrode mass loading for obtaining practically relevant areal capacities. Considering the vast possibilities of polymeric aromatic hydrocarbon compounds, specifically in terms of compositional and structural tunability, low cost, high abundance, and production scalability, this work provides further inspiration for the development of rechargeable aluminum batteries.

## Experimental Section

**Polymeric Cathode Materials:** Polypyrene was synthesized and purified according to the procedure reported by Li et al.<sup>[55]</sup> To synthesize poly(nitropyrene-co-pyrene), the same procedure was used with pyrene and 1-nitropyrene as starting materials in a 1:1 molar ratio. The resulting materials were further purified with acetonitrile and chloroform to completely remove unreacted 1-nitropyrene.

**Electrode Fabrication, Cell Assembly, and Electrochemical Measurements:** The following battery components were used: CB (Super C65, TIMCAL), poly(vinylidene fluoride) (PVdF, Sigma-Aldrich), *N*-methyl-2-pyrrolidone (NMP, 99%, Sigma-Aldrich), anhydrous AlCl<sub>3</sub> (99.99%, ABCR), 1-ethyl-3-methylimidazolium chloride ([EMIm]Cl, 99%, ABCR; dried at 130 °C under vacuum), and glass microfiber separator (GF/D, Whatman).

Electrodes were prepared by mixing the active material with PVdF and NMP using a Fritsch Pulverisette 7 classic planetary mill with zirconia beaker and 50 zirconia balls (5 mm in diameter) for 1 h at 500 rpm. The composition of the slurry was 50% pyrene-based polymer, 40% CB, and 10% PVdF. This fraction of CB was used to provide sufficiently high electrode conductivity. Slurries were coated onto tungsten current collectors (Alfa Aesar) and were dried at 80 °C for 12 h under vacuum (with loading of active material ≈0.5 mg cm<sup>-2</sup>). For measurements with pyrene, slurries were prepared using cyclopentanone instead of NMP as a solvent, and the current collectors were dried at room temperature for 12 h under vacuum. Electrochemical measurements were conducted in homemade, reusable, air-tight cells assembled in an Ar-filled glove box (O<sub>2</sub> < 0.1 ppm, H<sub>2</sub>O < 0.1 ppm) using 60 μL of AlCl<sub>3</sub>:[EMIm]Cl ionic liquid per cell. Aluminum foil (thickness: 11 μm) was used as both the reference and counter electrode. AlCl<sub>3</sub>:[EMIm]Cl ionic liquid was prepared by slowly mixing the [EMIm]Cl and AlCl<sub>3</sub> powders in an argon-filled glove box. Afterward, the ionic liquid was treated with Al foil at 150 °C for 6 h. A piece of glass fiber was used as the separator and dried overnight at 120 °C under vacuum prior to use. Galvanostatic cycling tests were carried out at room temperature with an MPG2 multichannel workstation (BioLogic). Capacities were normalized by the mass of the respective pyrene-based polymer.

**Materials Characterization:** Powder X-ray diffraction (XRD) was performed with a STOE STADI P powder X-ray diffractometer (Cu-Kα<sub>1</sub> irradiation, λ = 1.540598 Å). Scanning electron microscopy (SEM) measurements were collected using a NanoSEM 230. Attenuated total reflectance FTIR spectroscopy measurements were collected on a Nicolet iS5 FTIR spectrometer (Thermo Scientific). GPC was carried out using an Agilent GPC 1100 with tetrahydrofuran as the eluent. C, H, and N elemental analysis was carried out using a LECO TruSpec Micro. XPS measurements were carried out in normal emission using a monochromatized Al Kα X-ray radiation source and a Scienta R3000 display analyzer. EDX measurements were carried out using an EDAX Octane Super spectrometer (Ametek) attached to a Quanta 200F scanning electron microscope (Thermo Fisher Scientific).

## Supporting Information

Supporting Information is available from the Wiley Online Library or from the author.

## Acknowledgements

M.W. and K.V.K. contributed equally to this work. This work was financially supported by ETH Zürich (Grant Nr. ETH-56 12-2), the Swiss Federal Commission for Technology and Innovation (CTI-Project Nr. 14698.2 PFIW-IW), and CTI Swiss Competence Centers for Energy Research (SCCER Heat and Electricity Storage). The authors thank Beatrice Fischer and Prof. Dr. Frank Nüesch for GPC measurements and the microlaboratory at ETH Zürich for CHN analysis. The authors thank Dr. Frank Krumeich for EDX measurements. Electron microscopy was carried out at the Empa Electron Microscopy Center.

## Conflict of Interest

The authors declare no conflict of interest.

## Keywords

aluminum batteries, energy storage, polypyrenes, pyrene

Received: September 28, 2017

Revised: January 3, 2018

Published online: March 7, 2018

- [1] R. Van Noorden, *Nature* **2014**, 507, 26.
- [2] D. Larcher, J. M. Tarascon, *Nat. Chem.* **2015**, 7, 19.
- [3] H. Pan, Y.-S. Hu, L. Chen, *Energy Environ. Sci.* **2013**, 6, 2338.
- [4] M. D. Slater, D. Kim, E. Lee, C. S. Johnson, *Adv. Funct. Mater.* **2013**, 23, 947.
- [5] V. Palomares, P. Serras, I. Villaluenga, K. B. Hueso, J. Carretero-Gonzalez, T. Rojo, *Energy Environ. Sci.* **2012**, 5, 5884.
- [6] D. Aurbach, Z. Lu, A. Schechter, Y. Gofer, H. Gizbar, R. Turgeman, Y. Cohen, M. Moshkovich, E. Levi, *Nature* **2000**, 407, 724.
- [7] H. D. Yoo, I. Shterenberg, Y. Gofer, G. Gershinsky, N. Pour, D. Aurbach, *Energy Environ. Sci.* **2013**, 6, 2265.
- [8] M.-S. Park, J.-G. Kim, Y.-J. Kim, N.-S. Choi, J.-S. Kim, *Isr. J. Chem.* **2015**, 55, 570.
- [9] J. Muldoon, C. B. Bucur, T. Gregory, *Chem. Rev.* **2014**, 114, 11683.
- [10] I. Shterenberg, M. Salama, Y. Gofer, E. Levi, D. Aurbach, *MRS Bull.* **2014**, 39, 453.
- [11] T. Mori, Y. Orikasa, K. Nakanishi, C. Kezheng, M. Hattori, T. Ohta, Y. Uchimoto, *J. Power Sources* **2016**, 313, 9.
- [12] Z. Yu, Z. Kang, Z. Hu, J. Lu, Z. Zhou, S. Jiao, *Chem. Commun.* **2016**, 52, 10427.
- [13] S. Wang, Z. Yu, J. Tu, J. Wang, D. Tian, Y. Liu, S. Jiao, *Adv. Energy Mater.* **2016**, 6, 1600137.
- [14] N. Jayaprakash, S. K. Das, L. A. Archer, *Chem. Commun.* **2011**, 47, 12610.
- [15] H. Wang, Y. Bai, S. Chen, X. Luo, C. Wu, F. Wu, J. Lu, K. Amine, *ACS Appl. Mater. Interfaces* **2015**, 7, 80.
- [16] S. Gu, H. Wang, C. Wu, Y. Bai, H. Li, F. Wu, *Energy Storage Mater.* **2017**, 6, 9.
- [17] M. Chiku, H. Takeda, S. Matsumura, E. Higuchi, H. Inoue, *ACS Appl. Mater. Interfaces* **2015**, 7, 24385.
- [18] W. Wang, B. Jiang, W. Xiong, H. Sun, Z. Lin, L. Hu, J. Tu, J. Hou, H. Zhu, S. Jiao, *Sci. Rep.* **2013**, 3, 3383.
- [19] L. Geng, G. Lv, X. Xing, J. Guo, *Chem. Mater.* **2015**, 27, 4926.
- [20] M. P. Paranthaman, G. Brown, X.-G. Sun, J. Nanda, A. Manthiram, A. Manivannan, *Meet. Abstr.* **2010**, MA2010-02, 314.
- [21] S. Wang, S. Jiao, J. Wang, H.-S. Chen, D. Tian, H. Lei, D.-N. Fang, *ACS Nano* **2017**, 11, 469.
- [22] G. Cohn, L. Ma, L. A. Archer, *J. Power Sources* **2015**, 283, 416.
- [23] N. P. Stadie, S. Wang, K. V. Kravchyk, M. V. Kovalenko, *ACS Nano* **2017**, 11, 1911.
- [24] M.-C. Lin, M. Gong, B. Lu, Y. Wu, D.-Y. Wang, M. Guan, M. Angell, C. Chen, J. Yang, B.-J. Hwang, H. Dai, *Nature* **2015**, 520, 324.
- [25] L. Tan, Y. Chi-lung, *Int. Geol. Rev.* **1970**, 12, 778.
- [26] T. Jiang, M. J. Chollier Brym, G. Dubé, A. Lasia, G. M. Brisard, *Surf. Coat. Technol.* **2006**, 201, 10.
- [27] T. Jiang, M. J. Chollier Brym, G. Dubé, A. Lasia, G. M. Brisard, *Surf. Coat. Technol.* **2006**, 201, 1.
- [28] J. J. Auborn, Y. L. Barberio, *J. Electrochem. Soc.* **1985**, 132, 598.
- [29] P. K. Lai, M. Skyllas-Kazacos, *J. Electroanal. Chem. Interfacial Electrochem.* **1988**, 248, 431.
- [30] J. Muldoon, C. B. Bucur, T. Gregory, *Chem. Rev.* **2014**, 114, 11683.
- [31] J. Liu, Y. Wan, W. Liu, Z. Ma, S. Ji, J. Wang, Y. Zhou, P. Hodgson, Y. Li, *J. Mater. Chem. A* **2013**, 1, 1969.
- [32] A. Eftekhari, P. Corrochano, *Sustainable Energy & Fuels* **2017**, 1, 1246.
- [33] S. Wang, K. V. Kravchyk, F. Krumeich, M. V. Kovalenko, *ACS Appl. Mater. Interfaces* **2017**, 9, 28478.
- [34] Y. Wu, M. Gong, M.-C. Lin, C. Yuan, M. Angell, L. Huang, D.-Y. Wang, X. Zhang, J. Yang, B.-J. Hwang, H. Dai, *Adv. Mater.* **2016**, 28, 9218.
- [35] X. Yu, B. Wang, D. Gong, Z. Xu, B. Lu, *Adv. Mater.* **2017**, 29, 1604118.
- [36] G. Y. Yang, L. Chen, P. Jiang, Z. Y. Guo, W. Wang, Z. P. Liu, *RSC Adv.* **2016**, 6, 47655.
- [37] S. C. Jung, Y.-J. Kang, D.-J. Yoo, J. W. Choi, Y.-K. Han, *J. Phys. Chem. C* **2016**, 120, 13384.
- [38] Y. Gao, C. Zhu, Z. Chen, G. Lu, *J. Phys. Chem. C* **2017**, 121, 7131.
- [39] X. Huang, Y. Liu, H. Zhang, J. Zhang, O. Noonan, C. Yu, *J. Mater. Chem. A* **2017**, 5, 19416.
- [40] J. V. Rani, V. Kanakaiah, T. Dadmal, M. S. Rao, S. Bhavanarushi, *J. Electrochem. Soc.* **2013**, 160, A1781.
- [41] K. V. Kravchyk, S. Wang, L. Piveteau, M. V. Kovalenko, *Chem. Mater.* **2017**, 29, 4484.
- [42] M. Angell, C.-J. Pan, Y. Rong, C. Yuan, M.-C. Lin, B.-J. Hwang, H. Dai, *Proc. Natl. Acad. Sci. U. S. A.* **2017**, 114, 834.
- [43] Y. Song, S. Jiao, J. Tu, J. Wang, Y. Liu, H. Jiao, X. Mao, Z. Guo, D. J. Fray, *J. Mater. Chem. A* **2017**, 5, 1282.
- [44] S. Jiao, H. Lei, J. Tu, J. Zhu, J. Wang, X. Mao, *Carbon* **2016**, 109, 276.
- [45] H. Sun, W. Wang, Z. Yu, Y. Yuan, S. Wang, S. Jiao, *Chem. Commun.* **2015**, 51, 11892.
- [46] P. Bhauriyal, A. Mahata, B. Pathak, *Phys. Chem. Chem. Phys.* **2017**, 19, 7980.
- [47] Z. Song, H. Zhou, *Energy Environ. Sci.* **2013**, 6, 2280.
- [48] K. C. Kim, *Ind. Eng. Chem. Res.* **2017**, 56, 12009.
- [49] S. Muench, A. Wild, C. Friebe, B. Häupler, T. Janoschka, U. S. Schubert, *Chem. Rev.* **2016**, 116, 9438.
- [50] T. Nokami, T. Matsuo, Y. Inatomi, N. Hojo, T. Tsukagoshi, H. Yoshizawa, A. Shimizu, H. Kuramoto, K. Komae, H. Tsuyama, J.-i. Yoshida, *J. Am. Chem. Soc.* **2012**, 134, 19694.
- [51] N. S. Hudak, *J. Phys. Chem. C* **2014**, 118, 5203.
- [52] J. C. Bachman, R. Kaviani, D. J. Graham, D. Y. Kim, S. Noda, D. G. Nocera, Y. Shao-Horn, S. W. Lee, *Nat. Commun.* **2015**, 6, 7040.
- [53] S. C. Han, E. G. Bae, H. Lim, M. Pyo, *J. Power Sources* **2014**, 254, 73.
- [54] T. M. Figueira-Duarte, K. Müllen, *Chem. Rev.* **2011**, 111, 7260.
- [55] X.-G. Li, Y.-W. Liu, M.-R. Huang, S. Peng, L.-Z. Gong, M. G. Moloney, *Chem. - Eur. J.* **2010**, 16, 4803.
- [56] S. Califano, G. Abbondanza, *J. Chem. Phys.* **1963**, 39, 1016.
- [57] S. Zein El Abedin, *J. Solid State Electrochem.* **2012**, 16, 775.
- [58] J. M. Robertson, J. G. White, *J. Chem. Soc.* **1947**, 358.
- [59] H. D. B. Jenkins, K. P. Thakur, *J. Chem. Educ.* **1979**, 56, 576.
- [60] E. Pretsch, P. Bühlmann, C. Affolter, E. Pretsch, P. Bühlmann, C. Affolter, *Structure Determination of Organic Compounds*, Vol. 13, Springer, Berlin/Heidelberg, Germany **2009**.
- [61] C. Wang, H. Dong, W. Hu, Y. Liu, D. Zhu, *Chem. Rev.* **2012**, 112, 2208.